



TITLE:

# Observation of a Low-viscosity Interface Between Immiscible Polymer Layers

AUTHOR(S):

Hu, Xuesong; Lal, Jyotsana; Jiang, Zhang; Sinha, Sunil K.; Narayanan, Suresh; Sandy, Alec; Jiao, Xuesong; Lurio, Laurence B.

---

CITATION:

Hu, Xuesong ...[et al]. Observation of a Low-viscosity Interface Between Immiscible Polymer Layers. 物性研究 2006, 87(1): 184-185

ISSUE DATE:

2006-10-20

URL:

<http://hdl.handle.net/2433/110585>

RIGHT:

## Observation of a Low-viscosity Interface Between Immiscible Polymer Layers

Intense Pulsed Neutron Source, Argonne National Laboratory, Argonne, IL-60439, USA.

Xuesong Hu, Jyotsana Lal<sup>2</sup>

Department of Physics, University of California, San Diego, La Jolla, CA-92093, USA.

Zhang Jiang, Sunil K. Sinha<sup>2</sup>

Advanced Photon Source, Argonne National Laboratory, Argonne, IL-60439, USA.

Suresh Narayanan, Alec Sandy<sup>2</sup>

Department of Physics, Northern Illinois University, DeKalb, IL-60115, USA.

Xuesong Jiao, Laurence B. Lurio<sup>2</sup>

**Abstract:** X-ray Photon Correlation Spectroscopy (XPCS) was employed in a surface standing wave geometry in order to resolve the thermally diffusive in-plane dynamics at both the surface/vacuum (top) and polymer/polymer (bottom) interfaces of a thin Polystyrene (PS) film on top of Poly(4-bromo styrene) (PBrS) and supported on a Si substrate. The top vacuum interface shows two relaxation modes: one fast and one slow, while the buried polymer-polymer interface shows a single slow mode. The slow mode of the top interface is similar in magnitude and wavevector dependence to the single mode of the buried interface. The dynamics are consistent with a low-viscosity mixed layer between the PS and PBrS and coupling of the capillary wave fluctuations between this layer and the PS.

### 1 Introduction

Polymer/Polymer interfaces play an important role in the mechanical toughness of polymer blends, adhesion properties in coatings and co-extrusion of polymers. It has been reported that immiscible polymer blends can have viscosities lower than either of their components [1] and recent multilayer co-extrusion experiments indicate that the lower viscosity is due to interfacial slip [2]. Normally, interfaces between immiscible polymers exhibit poor adhesion [3] and this is attributed to weak entanglements between dissimilar polymers at an interface [4]. Dissipation within the interfacial regions can only be indirectly studied with bulk rheological measurements. Most results are in qualitative agreement with theories [4,5,6] that predict fewer chain entanglements near the interface between two immiscible polymers and thus a small interface width with lower viscosity. The lower viscosity at the interface explains slip on application of shear, however existing theories over-predict the slip effect [2]. Here we report on the development of a new technique, employing x-ray photon correlation spectroscopy [7] in a surface standing wave geometry [8,9], which provides a way to resolve the dynamics at buried polymer-polymer interface at nanoscale resolution both parallel and perpendicular to the interface.

### 2 Results and Discussion

In order to measure XPCS at a buried interface it is crucial to measure scattering from that interface alone, excluding possible scattering from the free surface or polymer-substrate interface. We have solved this problem by directing a coherent x-ray beam onto a polymer bilayer at grazing incidence so that a standing wave is set up in the sample. The phase of this standing wave can be adjusted to have a high intensity at the polymer-polymer interface and simultaneously a node at the polymer-air interface. In addition, at sufficiently grazing incidence angles, the x-rays do not penetrate to the substrate. Thus, the XPCS signal measured in this condition is an indication of the dynamics of the buried interface alone [8,9]. The sample we have chosen for this measurement is a polymer bilayer composed of a 100 nm polystyrene film on top of a 200 nm polybromostyrene film, supported on a Si substrate.

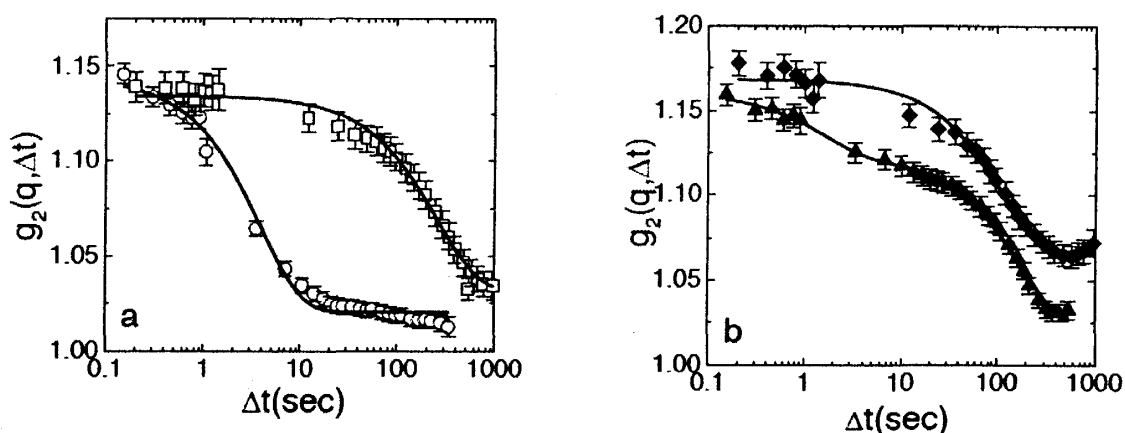


Figure 1: Auto-correlation functions from single and bilayer films at (a) 210°C ( $q=0.00405\text{nm}^{-1}$ ) PS single layer(○) and PBrS single layer(□) (b)210°C ( $q =0.00430\text{nm}^{-1}$ ) PS/PBrS top layer(▲) and PS/PBrS bottom layer(◆).

Figure 1b shows measured XPCS correlation functions for incident angles  $\theta_{in}=0.140^\circ$  and  $\theta_{in}=0.180^\circ$ , obtained from the PS/PBrS/Si film at 210°C. As can be seen from the Figure 1 at a fixed in-plane wavevector  $q=4.3 \times 10^{-3}\text{nm}^{-1}$  [8, 9] the scattering at  $\theta_{in}=0.140^\circ$  is due entirely to the top PS interface, while the scattering at  $\theta_{in}=0.180^\circ$  is dominated by the buried interface. The solid lines in Figure 1 represent the best single or double exponential fits to the measured autocorrelation at fixed value of  $q$ ,  $g_2(t)=1+B\sum_i a_i \exp(-2t/\tau_i)$ , where  $B$  is the speckle contrast and  $\tau_i$  is the relaxation time for equilibrium surface height fluctuations. The time constant for buried interface ( $\theta_{in}=0.180^\circ$ ) is found to be significantly slower than that of the top surface( $\theta_{in}=0.140^\circ$ ). The data from top and buried interface of the bilayer is compared to single layers of equivalent thickness at the same temperature (Figure 1a). In conclusion, have implemented a method for measuring diffuse scattering from each of the interfaces within a polymer bilayer, and shown that it is possible to measure XPCS independently at each interface, this has been measured as function of film thickness, wavevector and temperature.

**Acknowledgement** This work was supported by the U.S. Department of Energy, BES Materials Science, under contract W-31-109-ENG-38.

## References

- [1] C.D. Han and T.C. Yu, J. Appl. Polym. Sci, **15** (1971), 1163.
- [2] R. Zhao and C.W. Macosko, J. Rheo. **46**(1) (2002),145.
- [3] P.J. Cole, R.F. Cook and C.W. Macosko, Macromolecules **36** (2003), 2808.
- [4] R. Oslanec and H.R. Brown, Macromolecules, **36** (2003), 5839.
- [5] H. Furukawa, Phys. Rev. A **40**(11) (1989), 6403.
- [6] P.G. de Gennes, C.R. Acad, Sc. Paris, Serie B, t. **288** (1979), 219.
- [7] H. Kim *et. al.* , Phys. Rev. Lett. **90**(6) (2003), art. No.68302.
- [8]. L. B. Lurio, X. Hu S. Narayanan, X. Jiao and J. Lal, Mat. Soc. Symp. Proc. Vol. **790**@ 2004 Materials Research Society P7.43.1.
- [9] Xuesong Hu, Zhang Jiang, Suresh Narayanan, Xuesong Jiao, Alec Sandy, Sunil K. Sinha, Laurence B. Lurio and Jyotsana Lal to be published soon as Rapid Communication in Physical Review E.